

Solar Cell CIC Optimization and Factorization for CXBN-2

Lead Engineer:
Jacob R. Wade




Why?

Dicing solar cells can be an effective method of optimizing surface area and packing factor on CubeSats , while providing the necessary wattage.

CXBN2's solar panels will be tested to see if dicing solar cells and electrically connecting the string of diced cells in series will keep a positive power output for mission success.

Need to dice solar cells in order to achieve voltage matching for each string of cells.

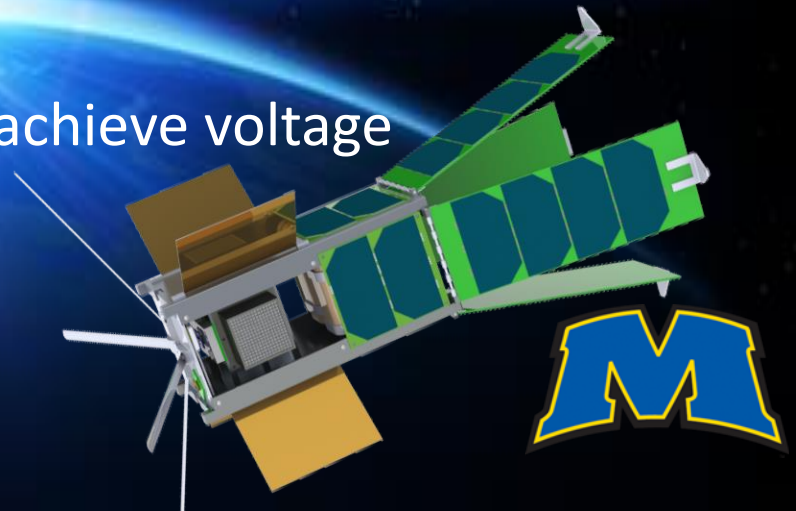

Purpose of CIC Dicing

CIC- Solar Cell Interconnects Coverglass

This project will involve dicing the solar cell CIC to satisfy the small satellite system requirements while having the most effective surface area and providing the necessary wattage.




CXBN-2 Solar Cell System

Original Mission


- Double fold out solar panels have a double hinge system

CXBN2 original solar array design

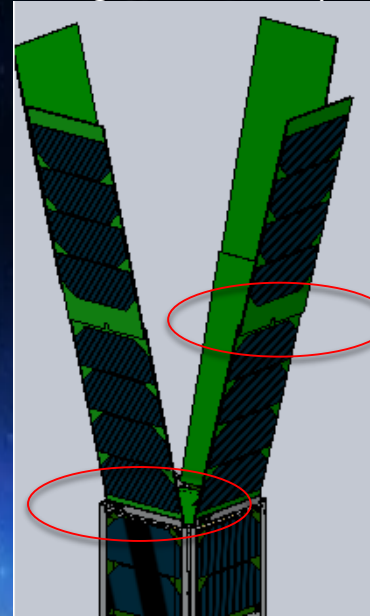

Single Fold Out Design


- Payload power requirement is less, each payload reduced to ~1 watt each.
- Less Risk
- Less Expensive

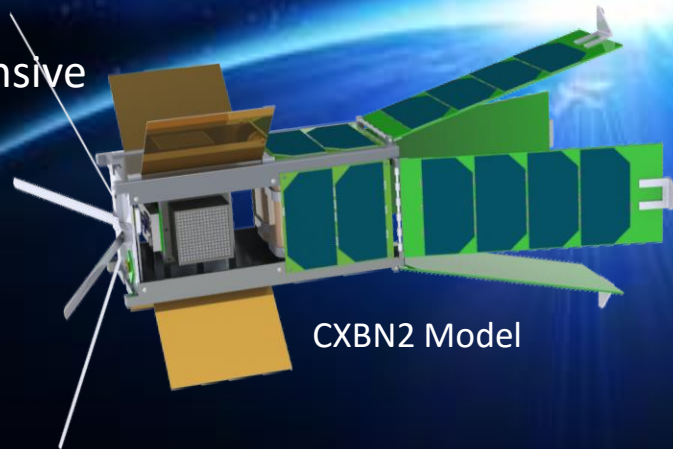

CXBN2 Model



Solar Cell

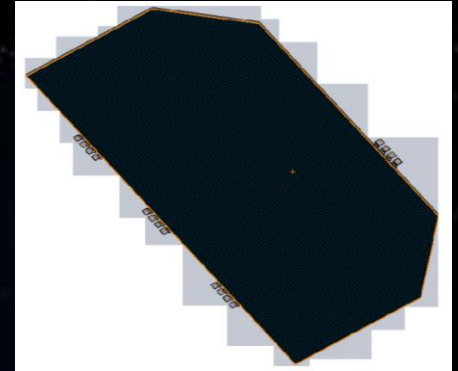

(Solid works Model)

- Solar Cells are from Azur Space.
- **Approximately 30% Triple Junction GaAs Solar Cell**
- Type: TJ Solar Cell 3G30C - Advanced
- Equipped with an integrated bypass diode, which protects the adjacent cell in the string.

Before Dicing Full Cell Test

Azure Space Data

Azure Space Solar Cell Testing					
Original Cell Data From Azure Space					
Date:	3/23/15				
		Isc mA	Voc V	Max Power	
Cell:	80361 1344 58	509.3	2.694	1372.0	mW
	80361 1344 60	512.5	2.713	1390.4	mW


Scale Factor from Azure Space Data sheet to testing procedures by a factor of 1.05.

Full Cell Data Before Dicing

Azure Space Solar Cell Testing					
Full Cell Test Data (Measured)					
Date:	3/23/15				
		Isc mA	Voc V	Max Power	
Cell:	80361 1344 58	489.5	2.46	1204.1 mW	
	80361 1344 60	502.3	2.48	1245.7 mW	



Solar Cell Before Dicing Dimensions

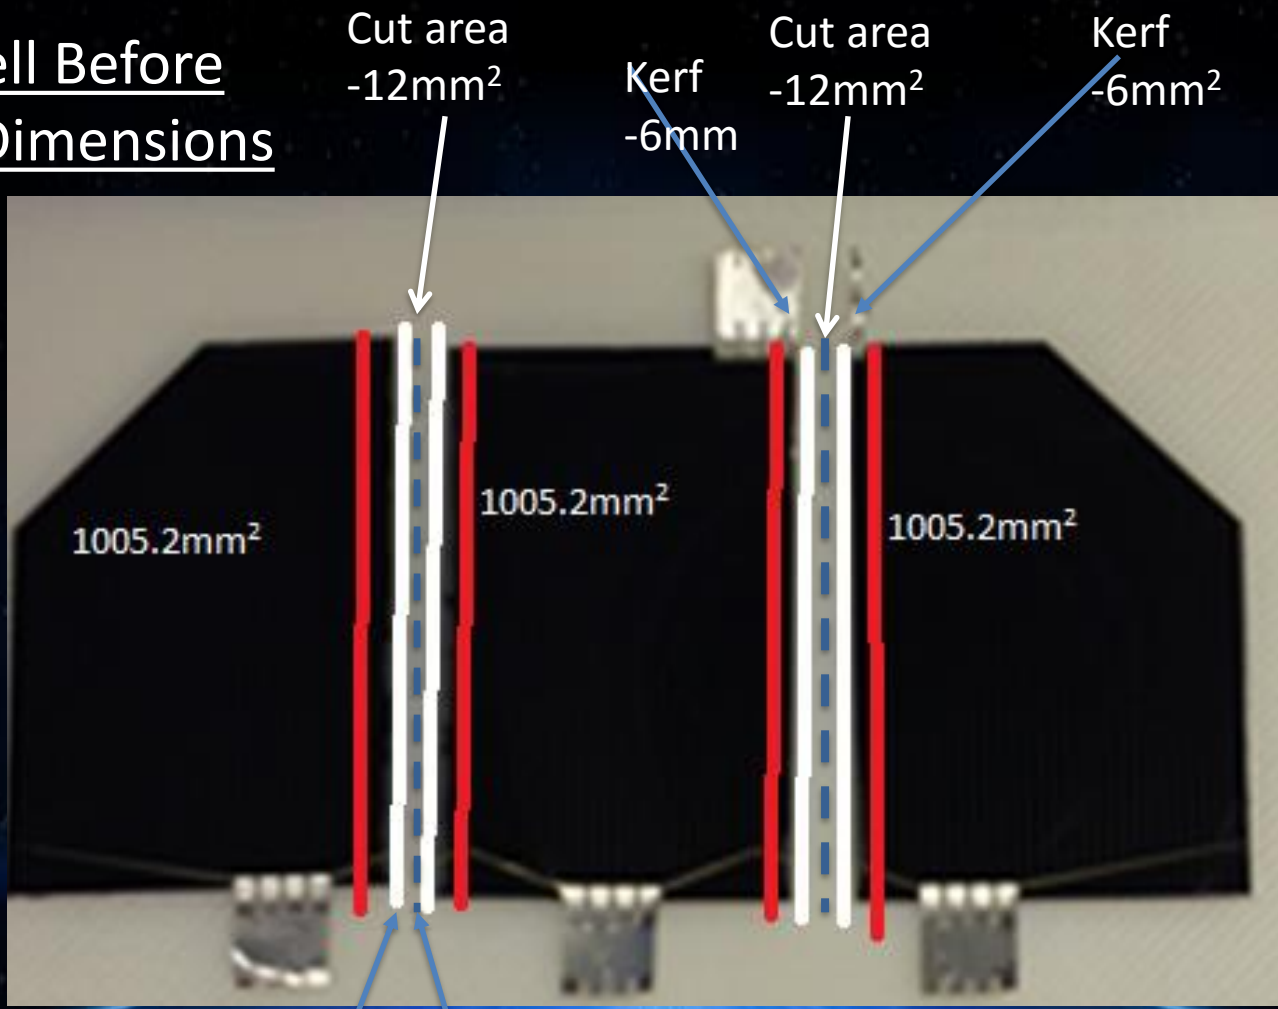

Kerf -6mm²

Kerf -6mm²

Solar Cell Dicing Process




Dicing Saw

Diamond embedded
dicing saw



Vacuum Chuck

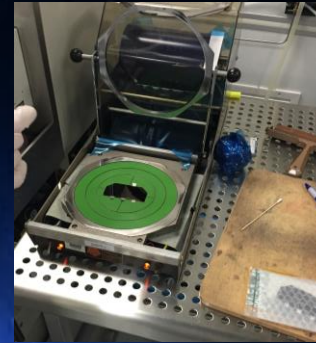

Entering in cutting dimensions


Work was performed at University of Louisville
Mico Nano Technology Center

Cutting the cells in two cuts and three pieces to
test efficiency.

CubeSats need specific cuts for maximum
surface area and to fit to design constraints.



After Dicing Dimensions

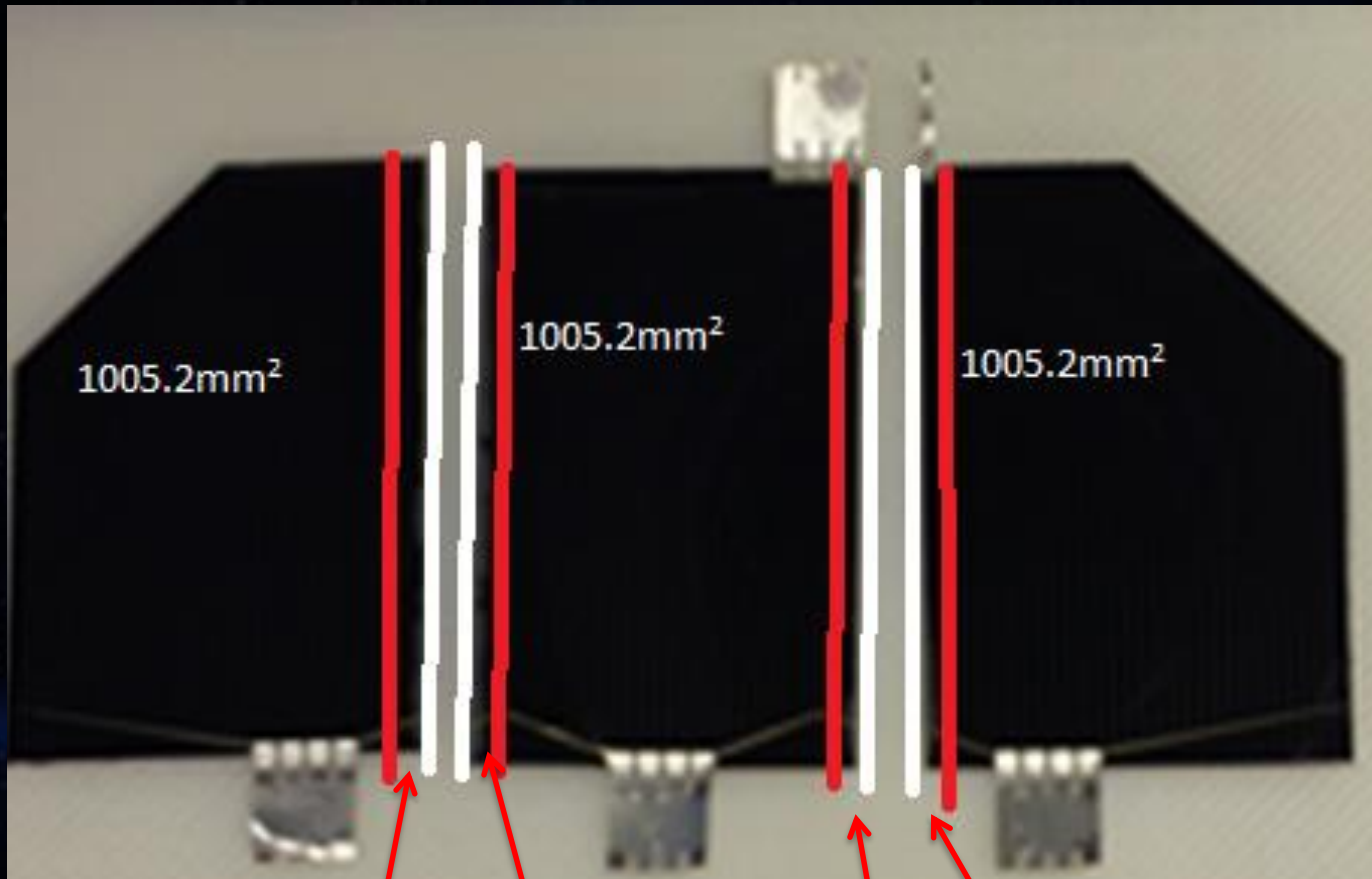


Fogged
Region
- 0.5mm²

Fogged
Region
- 0.5mm²


Fogged
Region
- 0.5mm²

Fogged
Region
- 0.5mm²

Solar Cell after dicing (backside)

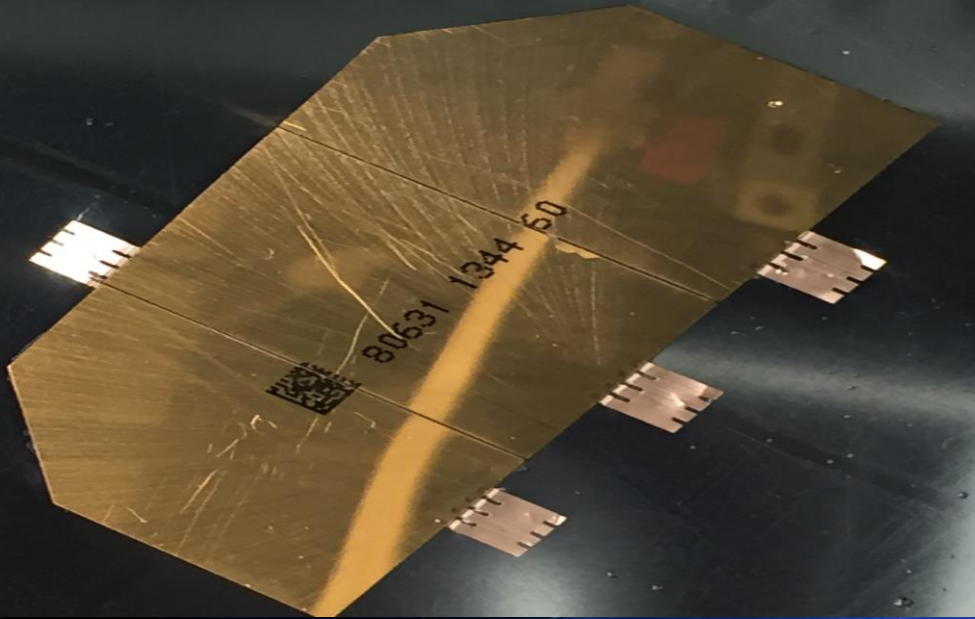

Solar Cell diced and snapped for separation (front side)

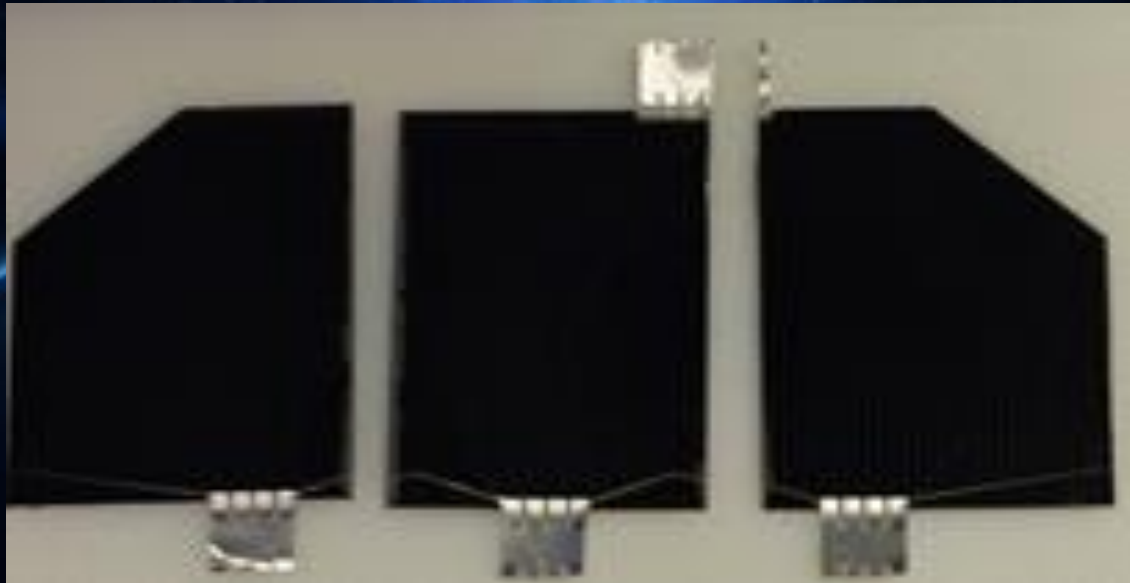



Full Solar Cell



Diced Solar Cell



Testing after dicing

Azure Space Solar Cell Testing

Original Cell Data From Azure Space

Cell:		Isc mA	Voc V	Max Power	
80361 1344 58		509.3	2.6	1372.0	mW
80361 1344 60		512.5	2.7	1390.4	mW

Azure Space Solar Cell Testing

Cut Cell Test Data (Measured)


Cell:		Isc mA	Voc V	Max Power	
80361 1344 58		169.6	7.8	1323.4	mW
80361 1344 60		170.6	7.6	1297.0	mW



Dicing Issues

Cell Chipping and Fogging along cuts.



What caused the fogging and cracking?

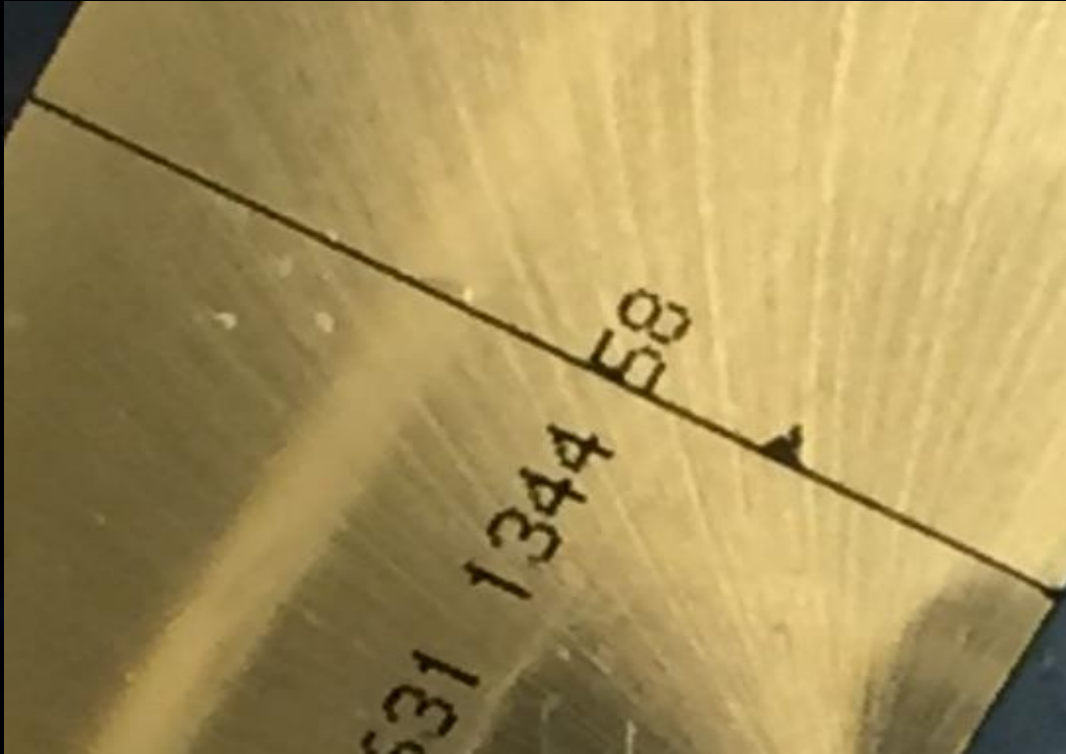


Chipped Cell after dicing



Solar Cell Cuts with fogging

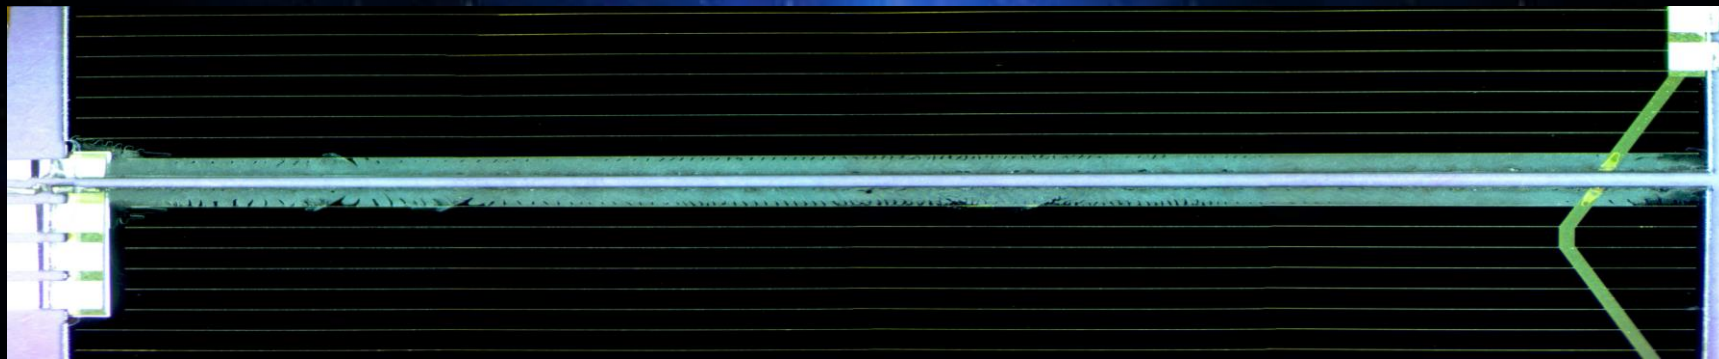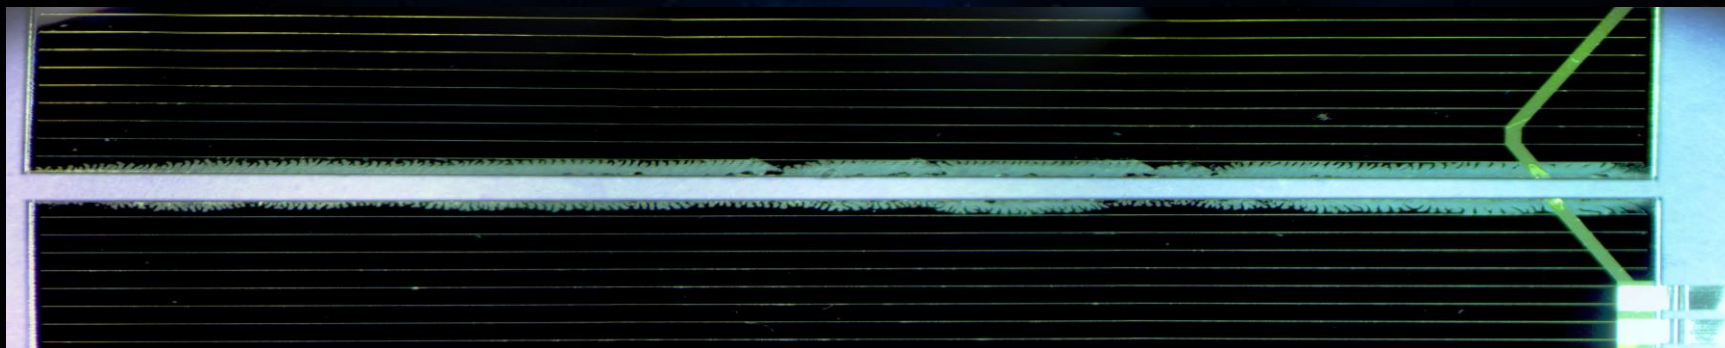

Cut
Direction



Possible Causes of fogging damage

- Speed rate of dicing saw.
- Vibrations from saw.
- Temperature increase.
- Water might not have been the best solution to dice with.
- Will thermal bake and vacuum remove fogging?



Testing at MSU

- After cells are diced they under went performance testing determining
- Power output and voltage max power, to Azure Space datasheet measured under AM0.
- Extrapolate Cut Cell Power Output @ AM0?
- Compare Efficiency of cells at max power.



Testing Model (Indoor and Outdoor)

Conditions:

Indoor under Halide and Flood lamps to simulate part of the visible light solar spectrum from 500nm-700nm.

Humidity= 0% Room Temp= 20°C

Outside: AM1.0-1.2;

Sunny (No Clouds)

Region Forecast- 26.6 - 31.6°C

Temp. Measured- 31.1°C

Humidity 88%

Wind @ 2MPH (TWC)

Time: 12:51 AM - 1:51 PM


Cells were placed onto 3D printed plates



Testing Performance after dicing at MSU

Solar Light Table- Uncalibrated but simulates solar spectrum inside.

Indoor Solar Light Table

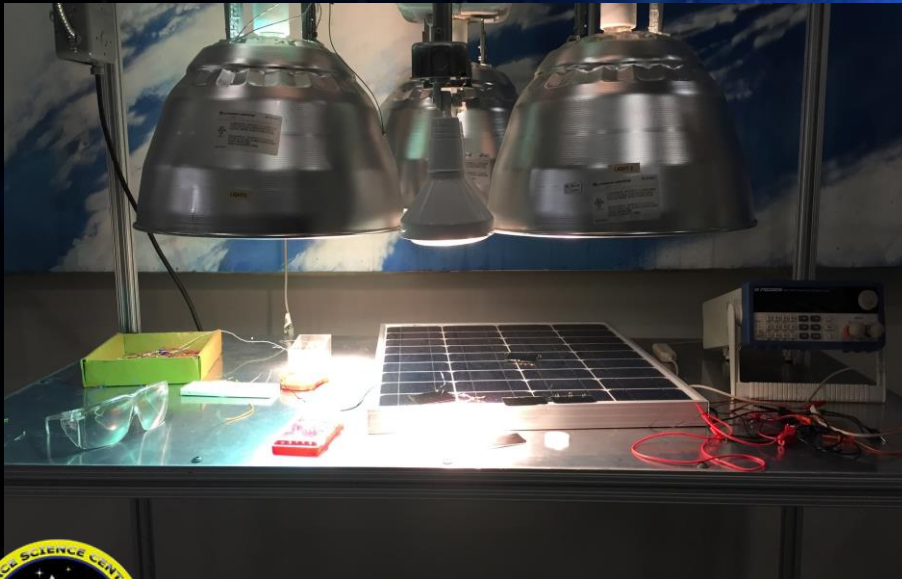

AM0

The spectrum outside the atmosphere, approximated by the 5,800 K black body, is referred to as "AM0", meaning "zero atmospheres". Solar cells used for space power applications, like those on communications satellites are generally characterized using AM0.


AM1

The spectrum after travelling through the atmosphere to sea level with the sun directly overhead is referred to, by definition, as "AM1". This means "one atmosphere". AM1 ($z=0^\circ$) to AM1.1 ($z=25^\circ$) is a useful range for estimating performance of solar cells in equatorial and tropical regions.




Testing Block Diagram

Indoor Solar Table

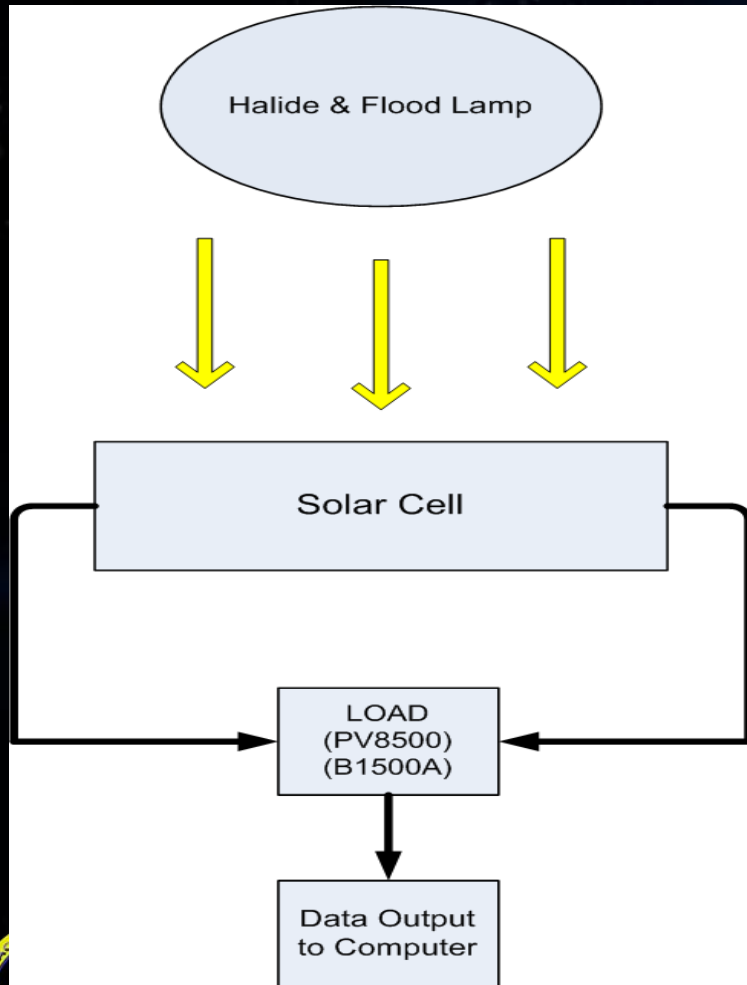


Outside testing

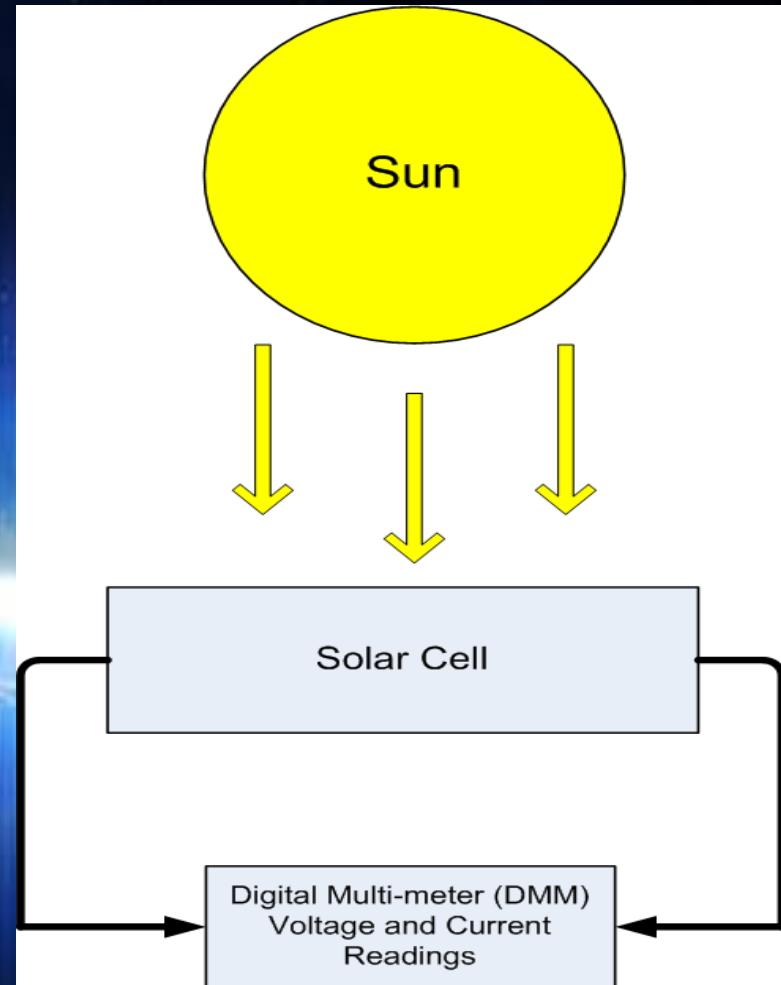

Power Output Results (AM1)

Full Cell Test 1
(2.2v,0.837W)


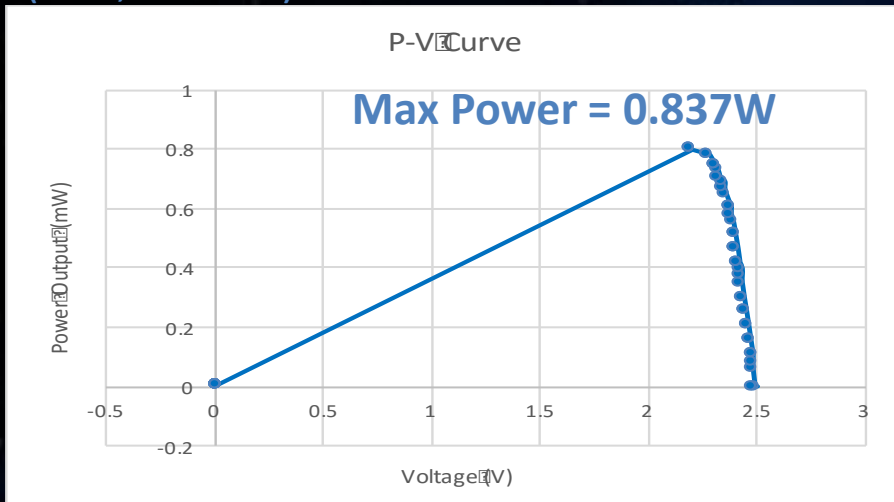


$$Cut_{AM0} = (Cut_{AM1.5}) * ((Full_{AM0}) / (Full_{AM1}))$$

$$Cut_{AM0} = (0.837W)(1.205W)/(0.812W)$$

$$Cut_{AM0} = 1.086W$$

Cut Cell Test Max Power Point-
(6.78v,0.732W)

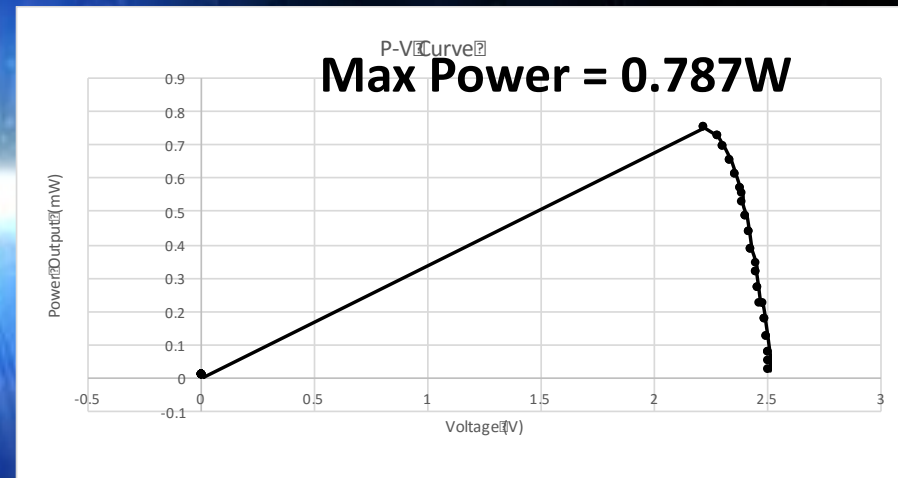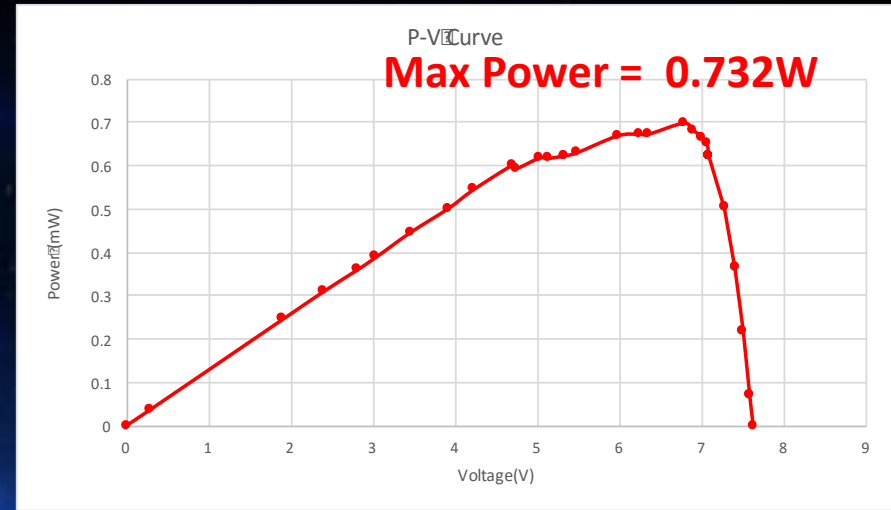

Full Cell Test 2-

(2.22v,0.787 W)



Thermal Vacuum Residual Gas Analysis Testing

Thermal Vacuum RGA test to determine the effect of the space environment on fogged regions on diced cells.

Start = Saturday, June 04, 2016

4:46:40 PM:000

Span = 4 Day(s) 20 Hour(s) 33 Min(s)
20 Sec(s)

Three Thermocouples (TC)

TC1– Between Aluminum plate and kapton Tape.

TC2- Cell #60 (Top Row)-Left Cut


TC3- Cell #58 (Bottom Row)-Right Cut

Other Measurements

Platen Temperature

Oven Temperature- 21.85°C - 80°C

Pressure– 9.3×10^{-7} Torr

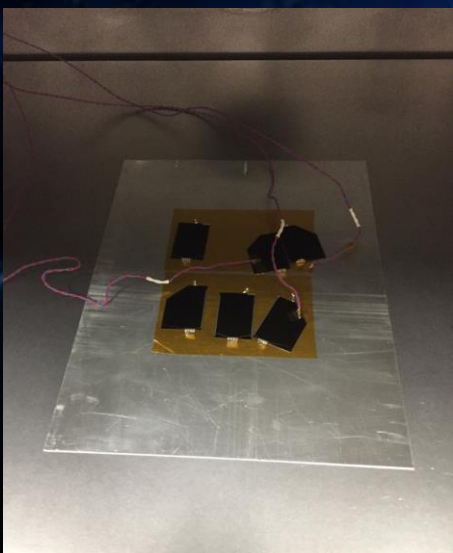

Test Conditions


Oven Max	63.6	°C
TC1 Max	100.8	°C
TC2 Max	98.6	°C
TC3 Max	101.8	°C
Platen Max	92.3	°C
Pressure	9.98E-07	Torr




Post TVAC Fogging Inspection Cut Cell




Left Cut

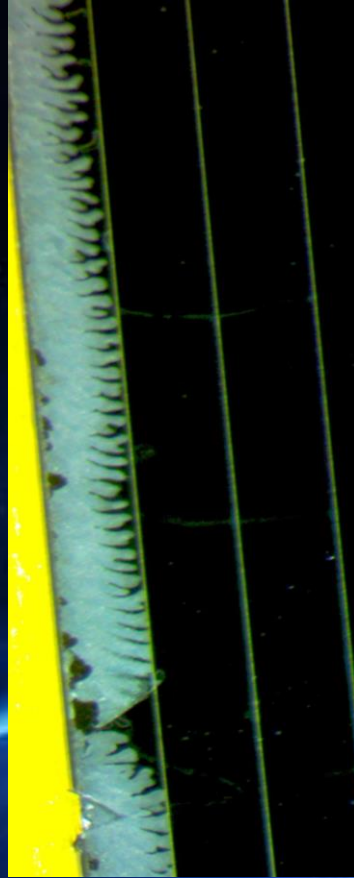

Left Center

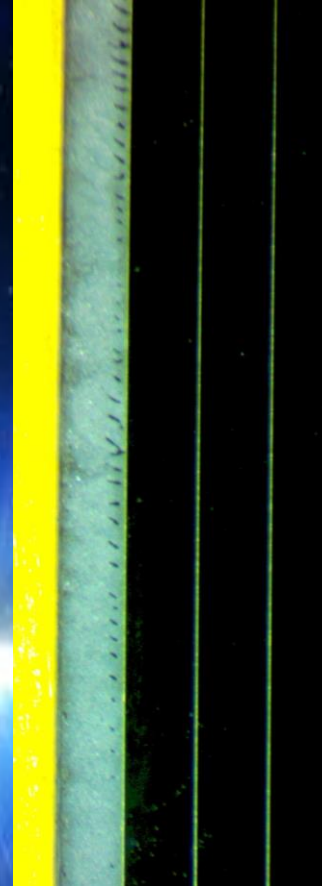

Right Center

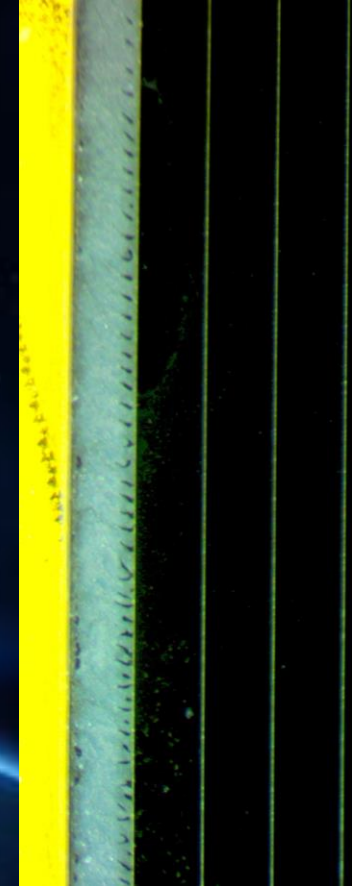

Right Cut



Full Cell vs Cut Cell CXBN2 Mission Requirements

- Full Cell is 29% efficient.
- Cut cell with no damage is 29% efficient.
- Cut cell at AM1.5 is ~28% due to fogging.
- Would have to connect two cells that are diced in series with fold out panel to keep solar array at max power output and solar efficiency.

Cut cells will provide more voltage at V_{mp} (Voltage Max Power) AM0 compared to full cell.



Conclusions

Dicing method is successful as long as the cut rate stays below 0.5mm/s.

Cut cells that are not damaged from dicing will keep the same efficiency and provide the mission requirements needed.

Fogging of cells is permanent damage, proof after environmental testing.



Questions/Comments

